



# **BEST PRACTICES FOR ACHIEVING GOOD FLOW AND CV WITH DRTS DRIPPERS**

DRIPPER PERFORMANCE GUIDE



## Introduction

When producing drip irrigation pipe two of the most important parameters to control are the dripper flow and the consistency of flow from dripper to dripper measured by the coefficient of variation (CV).

The flow can be adjusted by:

- Altering the pipe material composition (Raw Material type and mixture)
- Controlling the melt temperature of the pipe material through the flow process and temperatures of the extruders and the cross head
- Adjusting and controlling the dimensions of the crosshead tooling and to calibrator tooling dimensions (or drawdown) distance, and making sure wall thickness is balanced all around the pipe.
- Water temperature at the calibrator and water temperature at the vacuum tank,
- Vacuum tank pressure.

However, many of these parameters also have an effect on pipe dimensions which must meet a rigid standard so often there is a balancing between adjusting flow while achieving pipe parameters.

CV can be controlled by ensuring that the process is as controlled as possible and as stable as possible. More specifically it can be harmed by: high crosshead temperatures, overly high insertion speeds, misalignment of insertion to crosshead, large distance between crosshead and calibrator, non-concentric pipe, turbulence in the calibrator, inconsistent line speed, inconsistent pipe wall thickness, high clamping force from the puller, and mishandling or poor storage of the drippers.

This guide is intended to highlight some of the techniques to adjust flow, while maintaining a good CV with DRTS drippers.



### **A note on pipe material**

Pipe material can often play a large role in the process and each manufacturer develops a blend that meets their needs. Here is a starting point for pipe raw material many manufacturers start from.

55.5% LDPE – MFI 0.2g/ 10MIN (190:2.16 Kg) Density: 0.92 g/cm<sup>3</sup>

25% MDPE or HDPE – MFI 0.3g/ 10MIN (190:2.16 Kg) Density: 0.94 g/cm<sup>3</sup>

Elongation at break: > 600%

ESCR > 1000 HR

Tensile strength at break around 340 Kg/cm<sup>2</sup>

Tensile strength at yield around 210 Kg/cm<sup>2</sup>

Additives: No slip, no anti-block

15% LLDPE – MFI 1.0g/ 10MIN (190:2.16 Kg) Density 0.92 g/cm<sup>3</sup>

Elongation break: > 600%

Tensile strength at yield 115 Kg/cm<sup>2</sup>

Tensile strength at break 380 Kg/cm<sup>2</sup>

4.5% CARBON BLACK – Pigment content: 48% - 51%

MFI: 70 -120 g/10MIN (190:2.16 Kg)

Bulk density: 650 – 850 g/m

Particle size: nominal 60 NM

Additives: 0.25 Processing aid

0.20 Phenolic antioxidant

0.80 Phosphate antioxidant

### **Raw Material Suppliers**

#### **HELLER PERFORMANCE POLYMERS, INC.**

7227 Doe Avenue

Visalia, CA 93291

Tel: (559) 651-2091

Fax: (559) 651-2231

#### **EQUISTAR CHEMICALS, LP**

#### **EQUISTAR TECHNOLOGY CENTER**

11530 Northlake Drive

P.O. Box 429566

Cincinnati, OH 45249

Tel: (513) 530-4161 & (513) 530-4000

Fax: (513) 530-4284

#### **UNION CARBIDE CORPORATION**

950 South Coast Drive, Suite #145

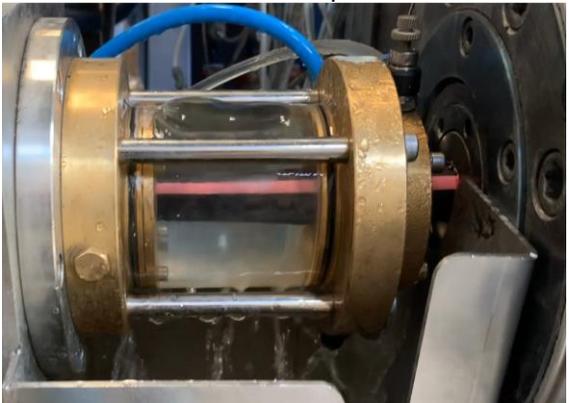
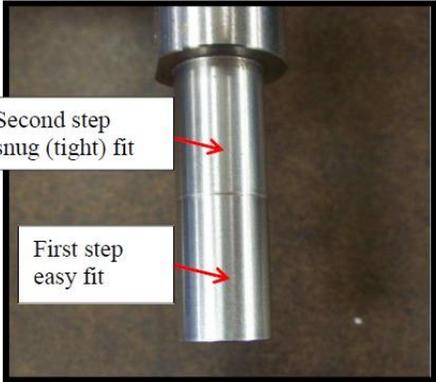
P.O. Box 5068

Costa Mesa, CA 92628

Tel: (562) 986-7925

Fax: (562) 986-7928

Customer Service: (800) 631-2555

<b>Subject</b>	<b>Guidance</b>	<b>Importance</b>
<p>1. Crosshead to Calibrator Distance</p> 	<p>Set to minimum. Ideally the length of a dripper or less (20-40mm)</p> <p>Distance should be repeatable</p>	<p>Larger distances generally means lower and less consistent flow and dripper spacing out of tolerance.</p> <p>In order to have a repeatable process.</p>
<p>2. Calibrator Crosshead Splash</p> 	<p>Make sure water is not splashing the crosshead</p> <p>Aquarium shouldn't spray the crosshead</p> <p>Splashguard should be sufficient.</p>	<p>Splash cools the pipe melt and affects consistency and bonding.</p>
<p>3. Pipe Inner Diameter (ID)</p>  	<p>For 16mm drippers Pipe ID: 13.8-14.0 mm</p> <p>For 18mm drippers Pipe ID: 16.7-17.0 mm</p> <p>For 20mm drippers Pipe ID: 17.6 mm</p>	<p>A smaller pipe ID reduces flow. A larger pipe ID increases flow. Pipe ID should be set according to market standards. Use a stepped tool [pictured] to quickly check ID before starting dripline production.</p>

<p>4. Vacuum Stability</p> 	<p>Vacuum must be absolutely stable</p>	<p>Vacuum is used to adjust dripper flow. Stronger vacuum means higher flow. Stable vacuum means stable flow.</p>
<p>5. Water Temperatures</p>	<p>Recommended gauge range: -15 to -40mbar</p>	<p>Water temp in the Calibrator 15-25°C (lower temp for higher line speed)</p>
<p>6. Pipe Centricity and Wall Thickness</p> 	<p>Water temp in the vacuum tank can be a few degrees colder than the Calibrator.</p>	<p>It can be helpful to have the Calibrator warmer than the Vacuum Tank. If the vacuum is too cold it will shock freeze the pipe. Too warm and the pipe won't cure properly.</p> <p>Wall thickness should be measured consistent at 4-6 points around the circumference of the pipe. Mark the pipe at the top to assist in adjustments.</p> <p>Uneven pipe can cause flow variations.</p>

### 7. Material Melt Temperature



Melt temperature can be controlled at the Crosshead zone. Too high and the labyrinth is melted. Too low and the bonding is incomplete.

Labyrinth should be bonded to the pipe but not overly melted which causes a mushroom effect on the labyrinth teeth [top picture]. When the pipe is too cold bonding is incomplete [bottom picture]

### 8. Haul-Off Compression



Make sure the haul-off/puller of the pipe does not smash the drippers. It should be adjusted to a minimum that consistently pulls the pipe. V grooved belt on the haul-off is recommended.

Too much compression on the drippers from the Haul-Off can cause low flow and inconsistency. DRTS uses a unique hauloff design that regulated the pressure with air as well as use a floating belt mechanism to reduce the pressure on the dripline.

9. Perforator Depth



Make sure that the Perforator drilling of the pipe is not scratching the dripper pool.

Even minor scratch marks indicate the occasional possibility for small punctures in the dripper which greatly increases flow.